

TECHNICAL SPECIFICATION



Test methods for electrical materials, printed boards and other interconnection structures and assemblies –
Part 3-301: Test methods for interconnection structures (printed boards) –
Appearance inspection method for plated surfaces on PWB



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2016 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

IEC Catalogue - webstore.iec.ch/catalogue

The stand-alone application for consulting the entire bibliographical information on IEC International Standards, Technical Specifications, Technical Reports and other documents. Available for PC, Mac OS, Android Tablets and iPad.

IEC publications search - www.iec.ch/searchpub

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and also once a month by email.

Electropedia - www.electropedia.org

The world's leading online dictionary of electronic and electrical terms containing 20 000 terms and definitions in English and French, with equivalent terms in 15 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

65 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: csc@iec.ch.

IECNORM.COM : Click to view the full PDF IEC 61899-3301:2016

TECHNICAL SPECIFICATION



**Test methods for electrical materials, printed boards and other interconnection structures and assemblies –
Part 3-301: Test methods for interconnection structures (printed boards) –
Appearance inspection method for plated surfaces on PWB**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 31.180

ISBN 978-2-8322-3550-8

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	3
1 Scope.....	5
2 Normative references.....	5
3 Terms and definitions	5
4 Test specimens	5
5 Equipment / apparatus.....	5
5.1 Evaluation of lustre non-uniformity.....	5
5.2 Evaluation of colour non-uniformity.....	6
6 Procedure	6
6.1 Outline of the method	6
6.2 Specimen preparation	6
6.3 Imaging of surface roughness/chromaticity distribution.....	6
6.4 Binarization of images	6
6.5 Extraction of feature quantities	7
6.6 Derivation of discriminant function	7
6.7 System registration	7
7 Report.....	8
8 Additional information	8
Annex A (informative) Example of equipment and tested result for lustre non-uniformity	9
A.1 Equipment for lustre non-uniformity inspection.....	9
A.2 Tested result.....	9
A.2.1 Surface roughness image.....	9
A.2.2 Binarized image and feature extraction.....	11
A.2.3 Frequency analysis of feature quantities.....	12
A.2.4 Final estimate	12
Annex B (informative) Example of tested result for colour non-uniformity inspection	13
B.1 Image analysis of colour non-uniformity	13
B.2 Feature extraction and discriminant analysis.....	14
Bibliography	16
Figure 1 – Flow chart of the test procedure.....	6
Figure A.1 – Equipment prototype	9
Figure A.2 – Images of gold-plating of non-defective and defective products	10
Figure A.3 – Images of S- and P-polarized components, and Ψ' for gold-plating with lustre non-uniformity	11
Figure A.4 – Image examples of gold-plating with lustre non-uniformity	11
Figure A.5 – Example of frequency analysis of feature quantity.....	12
Figure A.6 – Example of the final estimate of the quality of gold-plating	12
Figure B.1 – Images of gold-plating pads.....	13
Figure B.2 – Images of colour distribution.....	14
Figure B.3 – Frequency analysis example of a feature quantity	14
Figure B.4 – Example of the discriminant analysis result.....	15

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**TEST METHODS FOR ELECTRICAL MATERIALS, PRINTED BOARDS AND
OTHER INTERCONNECTION STRUCTURES AND ASSEMBLIES –****Part 3-301: Test methods for interconnection structures (printed boards) –
Appearance inspection method for plated surfaces on PWB**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

The main task of IEC technical committees is to prepare International Standards. In exceptional circumstances, a technical committee may propose the publication of a technical specification when

- the required support cannot be obtained for the publication of an International Standard, despite repeated efforts, or
- the subject is still under technical development or where, for any other reason, there is the future but no immediate possibility of an agreement on an International Standard.

Technical specifications are subject to review within three years of publication to decide whether they can be transformed into International Standards.

IEC TS 61189-3-301, which is a technical specification, has been prepared by IEC technical committee 91: Electronics assembly technology.

The text of this technical specification is based on the following documents:

Enquiry draft	Report on voting
91/1348/DTS	91/1376/RVC

Full information on the voting for the approval of this technical specification can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 61189 series, published under the general title *Test methods for electrical materials, printed boards and other interconnection structures and assemblies*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- transformed into an International standard,
- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

TEST METHODS FOR ELECTRICAL MATERIALS, PRINTED BOARDS AND OTHER INTERCONNECTION STRUCTURES AND ASSEMBLIES –

Part 3-301: Test methods for interconnection structures (printed boards) – Appearance inspection method for plated surfaces on PWB

1 Scope

This part of IEC 61189 outlines a way to determine the appearance non-uniformity of both the lustre and colour on plated metal surfaces in printed wiring boards (PWBs). The method is applicable to gold, nickel and copper plating in PWBs.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

lustre non-uniformity

abnormal roughness distribution in plated surfaces leading to irregular brightness of reflected light

3.2

colour non-uniformity

irregular reflection spectrum

Note 1 to entry: Colour non-uniformity is caused by other influences than roughness change, such as abnormal components, adhesion of foreign matter and oxidation in plated surfaces.

4 Test specimens

4.1 Specimen dimensions and forms should be in accordance with the test system.

4.2 Specimens of non-defective and of defective products, of several tens to one hundred, at least of ten, are required as teacher data for each series of evaluation.

5 Equipment / apparatus

5.1 Evaluation of lustre non-uniformity

For the evaluation of the lustre non-uniformity, a test system capable of measuring the surface roughness distribution should be used. As for an optical method, CCD (charge-

coupled device), or CMOS (complementary metal oxide semiconductor) camera systems, or as for a mechanical method, stylus type tester shall be used, respectively.


5.2 Evaluation of colour non-uniformity

For the evaluation of the colour non-uniformity, an optical system capable of measuring the chromaticity distribution shall be used.

6 Procedure

6.1 Outline of the method

The method is outlined by the flow chart in Figure 1.

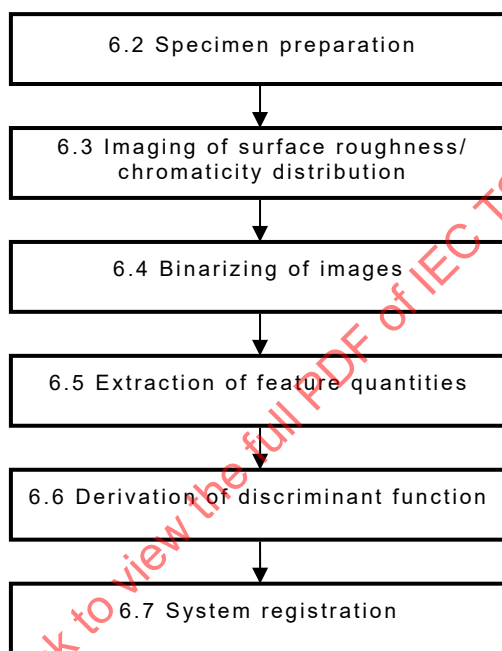

IEC

The numbers indicate the subclause references.

Figure 1 – Flow chart of the test procedure

In this method, the procedures of the evaluation of lustre non-uniformity and colour non-uniformity are basically the same.

6.2 Specimen preparation

Requirements for specimens are specified in Clause 4.

6.3 Imaging of surface roughness/chromaticity distribution

Acquire the images of surface roughness for the lustre non-uniformity, and/or of chromaticity distribution for the colour non-uniformity, by the apparatus / equipment mentioned in Clause 5.

6.4 Binarization of images

Obtain the binary images by the threshold processing. The region giving values significantly deviating from the average value of the whole image concerned is counted to be 1 (white pixels) as abnormal, and the others to be 0 (black pixels) as normal.

The threshold setting should be agreed upon between the parties.

6.5 Extraction of feature quantities

Extract the feature quantities of abnormal regions from the binarized images by image analysis of the size, area, shape, and distribution, etc. of the irregularities.

For example, the diagonal length of the minimum rectangles bounding the clusters of abnormal regions, and change in the number of pixels by the binary image contraction of repetition can be used as feature quantities.

The type and number of feature quantities to be used should be agreed upon between the parties.

6.6 Derivation of discriminant function

Discriminant analysis shall be performed using the feature quantities extracted from specimens of non-defective and defective products as indicated in 6.5 as the teacher data to split into two groups.

The linear discriminant function is expressed by Equation (1):

$$Z = a_0 + a_1X_1 + a_2X_2 + a_3X_3 + \cdots + a_iX_i + \cdots \quad (1)$$

where

Z is the discriminant score;

a_0 is a constant;

i (subscript) indicates the dimensions of the discriminant function;

a_i is the discriminant coefficient as weighting factor for the separation of test specimens of teacher data into the two groups, non-defective and defective;

X_i is the frequency of feature quantities taken into consideration.

Equation (1) is defined to distinguish the group of non-defective specimens from the group of defective specimens by the value Z , which is respectively set to be positive for non-defective and negative for defective specimens by adjusting a_i , and a_0 .

If necessary, the type of non-linear discriminant function based on Mahalanobis' generalized distance, D^2 may also be used.

The type of the discriminant function to be used can be agreed upon between the parties.

6.7 System registration

The resulting discriminant function shall be registered to the test system to perform evaluation of unknown specimens.

For the unknown specimen, the value of Z shall be calculated using the registered function, which is defined by Equation (1) in advance in the linear discriminant analysis.

From the values of Z obtained, the quality of the unknown specimen can be estimated.

In case of a non-linear discriminant function, the values of D^2 shall be used for the estimate of unknown specimens.

7 Report

7.1 Report the specimen numbers of both non-defective and defective products used as the teacher data.

7.2 Report the apparatus / equipment information for capturing images of plated surfaces in the tested specimens.

7.3 Report the value of threshold for the binarizing images.

7.4 Report the type, stepping width, and range of the feature quantities extracted from the binarized images.

7.5 Report the discriminant function derived for evaluation of the tested specimens.

8 Additional information

8.1 An optical method based on the polarization analysis and image recognition has been proposed from AIST, Japan, and a powerful camera system that can observe both a lustre irregularity and uneven colouring at the same time has been developed.

8.2 Examples of the equipment and tested results are shown in Annex A and Annex B.

IECNORM.COM : Click to view the full PDF of IEC TS 61189-3-301:2016

Annex A (informative)

Example of equipment and tested result for lustre non-uniformity

A.1 Equipment for lustre non-uniformity inspection

Figure A.1 shows the test equipment prototyped for the lustre non-uniformity.

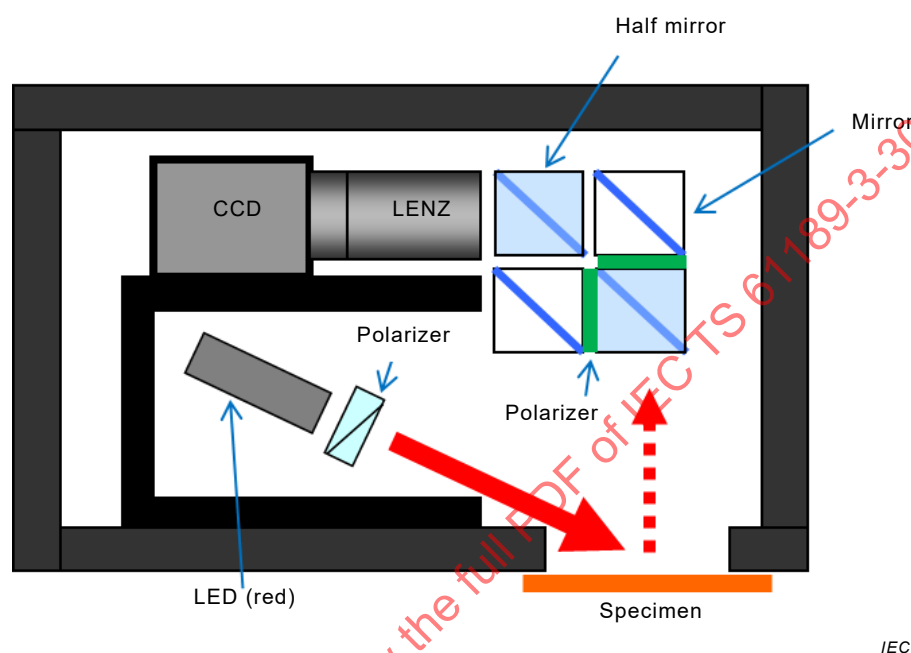


Figure A.1 – Equipment prototype

The incident light that illuminated the sample was linearly polarized and tilted at 45° to have the ratio of 1/1 for the S-/P-polarized components. The reflected light was separated by a half mirror and passed the S and P polarizers for independent imaging by the CCD camera. In order to obtain distribution images of the surface roughness, the CCD images captured were analyzed by comparing each pixel of the images of the S- and P-polarized components.


Mapping of the surface roughness according to the pixel size can be achieved using this method.

A.2 Tested result

A.2.1 Surface roughness image

Figure A.2 shows the examples of images of gold-plated pads of non-defective (see a to c) and defective products (see d to l) with various types of lustre non-uniformity in PWBs, captured by a CCD camera.

Figure A.3 shows the example of surface roughness images analyzed by the equipment of Figure A.1 for gold plating of defective specimens with lustre non-uniformity. Images of S-polarized (see a, d, g), P-polarized (see b, e, h) components, and Ψ' (see c, f, i), calculated from the ratio of S- to P-polarized components indicate the surface roughness distribution for gold-plating with lustre non-uniformity in PWBs.

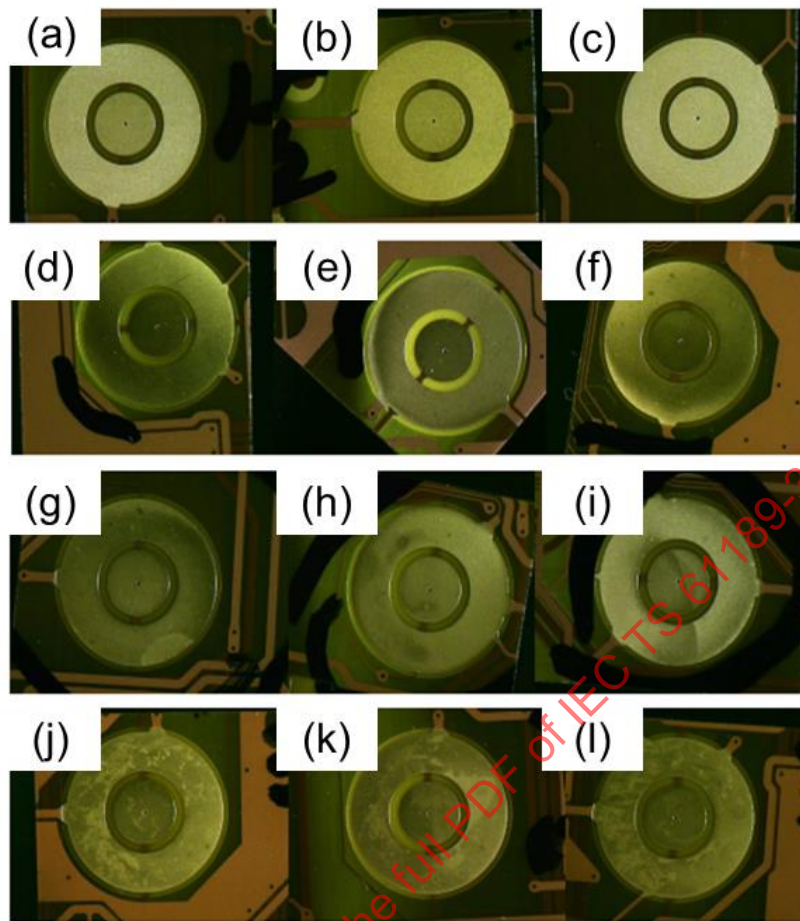

IEC

Figure A.2 – Images of gold-plating of non-defective and defective products

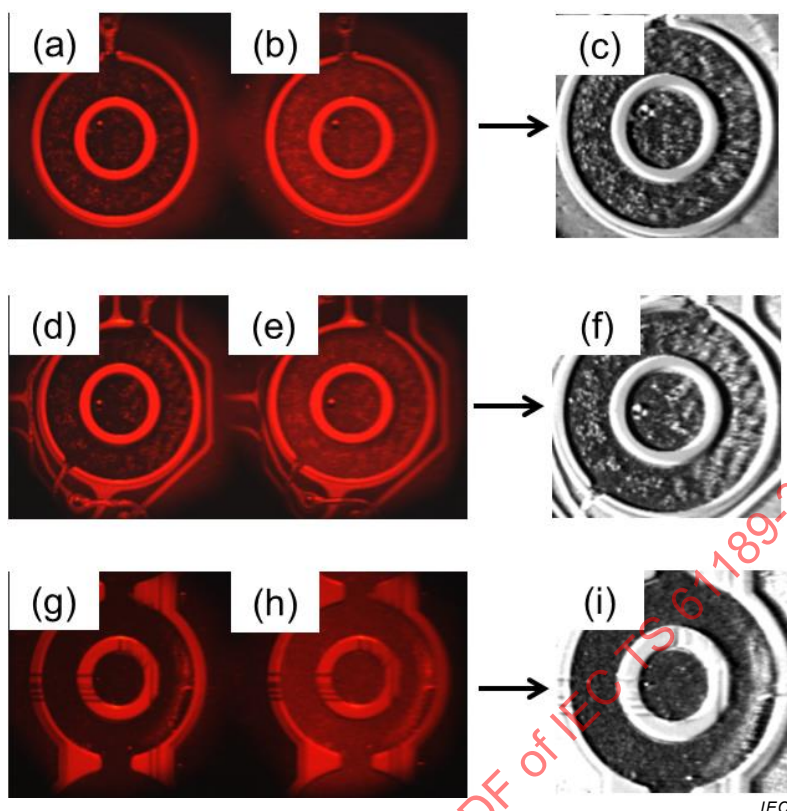


Figure A.3 – Images of S- and P-polarized components, and Ψ' for gold-plating with lustre non-uniformity

A.2.2 Binarized image and feature extraction

Figure A.4 a) shows an example of a binarized image of abnormal portions in the series of specimens shown in Figure A.2 and Figure A.3. The threshold for binarization is set as follows: regions giving values within $\pm 10\%$ of the average value are classified as normal, and those beyond this limit are counted as abnormal (white pixels).

Figure A.4 b) shows an example of extraction of feature quantities of abnormal portions using the minimum rectangles bounding the clusters of white pixels. The diagonal length of the minimum rectangles is defined as the feature quantity, expressed as L_i .

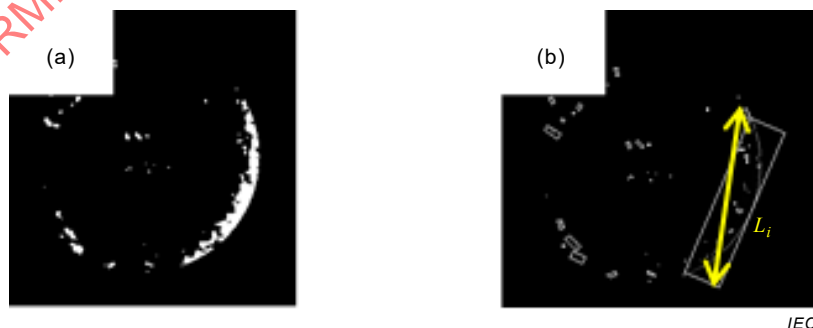



Figure A.4 a) – Binarized image

Figure A.4 b) – Feature quantity

Figure A.4 – Image examples of gold-plating with lustre non-uniformity

A.2.3 Frequency analysis of feature quantities

Figure A.5 shows an example of a frequency analysis of the feature quantities of gold-plating L_i to obtain each frequency, X_i .

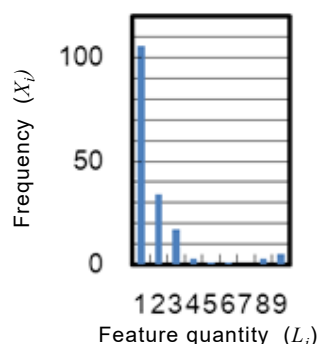


IEC

Figure A.5 – Example of frequency analysis of feature quantity

A.2.4 Final estimate

Figure A.6 shows an example of the linear discriminant analysis result using specimens of gold-plating of non-defective and defective products as the teacher data to determine the quality of the object specimens corresponding to boundary specimens.

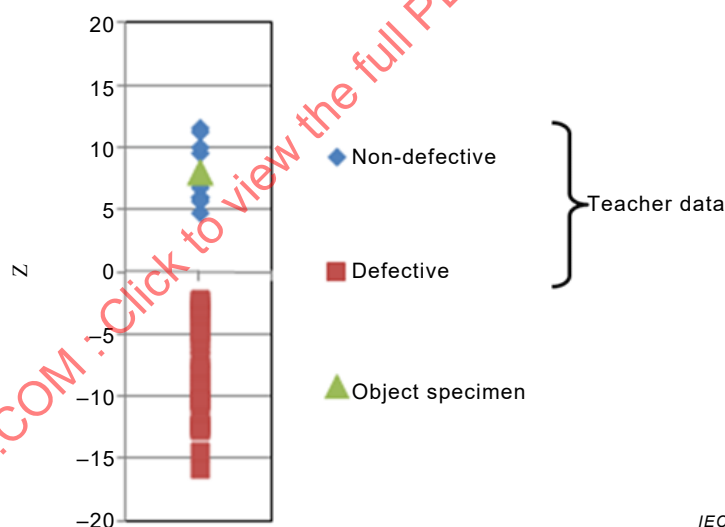

IEC

Figure A.6 – Example of the final estimate of the quality of gold-plating

As shown in Figure A.6, Z of a non-defective product takes a value above 0, in the range +5 to +12. In contrast, Z of a defective product takes a value below 0, in the range –2 to –16. Using this function, Z of an unknown (object) specimen is evaluated to be 7, and this result estimates the specimen as non-defective, and the judgment agrees with that obtained by visual inspection.

In this way, the criteria for acceptability can be provided using the discriminant function. As a result, objective determination and classification criteria can be obtained for the digitization of the lustre non-uniformity of gold plating.

Annex B (informative)

Example of tested result for colour non-uniformity inspection


B.1 Image analysis of colour non-uniformity

Colour non-uniformity has been analyzed using the ratios of different colour signal settings such as green to red (G/R), blue to green (B/G), and red to blue (R/B) in images captured by a CCD camera for gold-plating pads in defective specimens of PWB.

Figure B.1 shows an example of a result of colour non-uniformity analysis using the ratio of G/R, which gives the clearest change (comparing to the ratios of B/G and R/B in this experiment).

The images of Figure B.1 display the following gold-plating pads (500 μm $\times$ 500 μm)

- colour non-uniformity,
- the magnified view,
- and the colour distribution in G/R, with the signal intensity ratio of green to red, as a function of pixel position in a CCD camera.

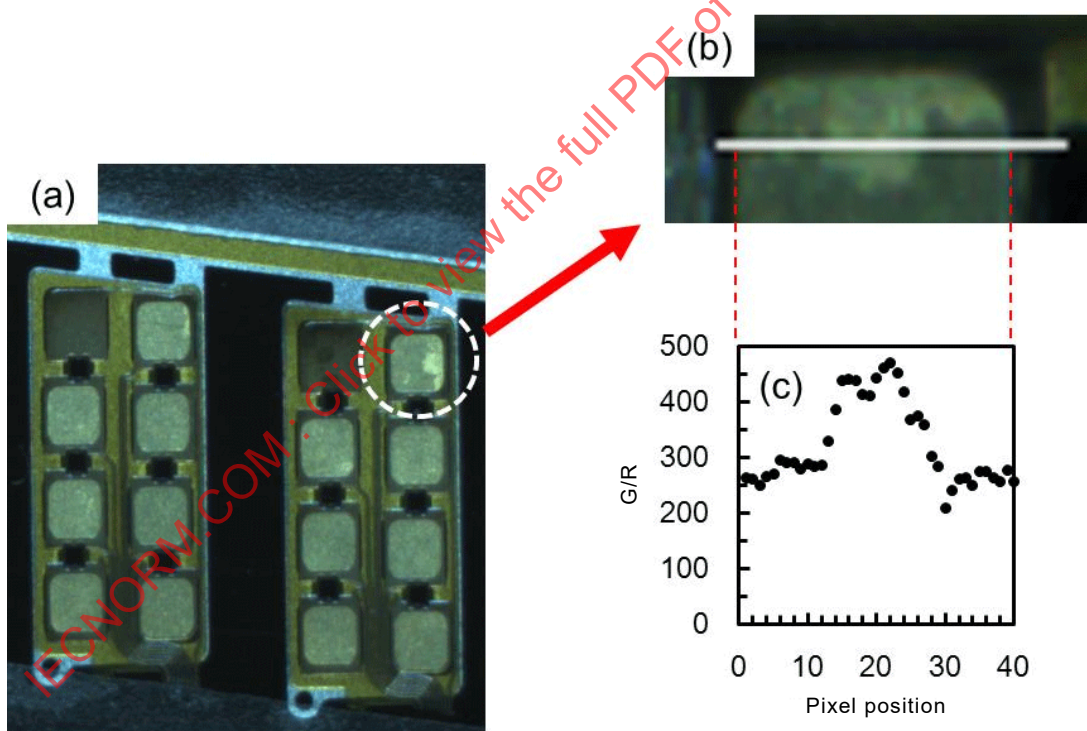

IEC

Figure B.1 – Images of gold-plating pads

Figure B.2 shows the examples of images of G/R and threshold images for the same specimen as shown in Figure B.1. In Figure B.2 b), the regions detected as colour non-uniformity are marked in red.

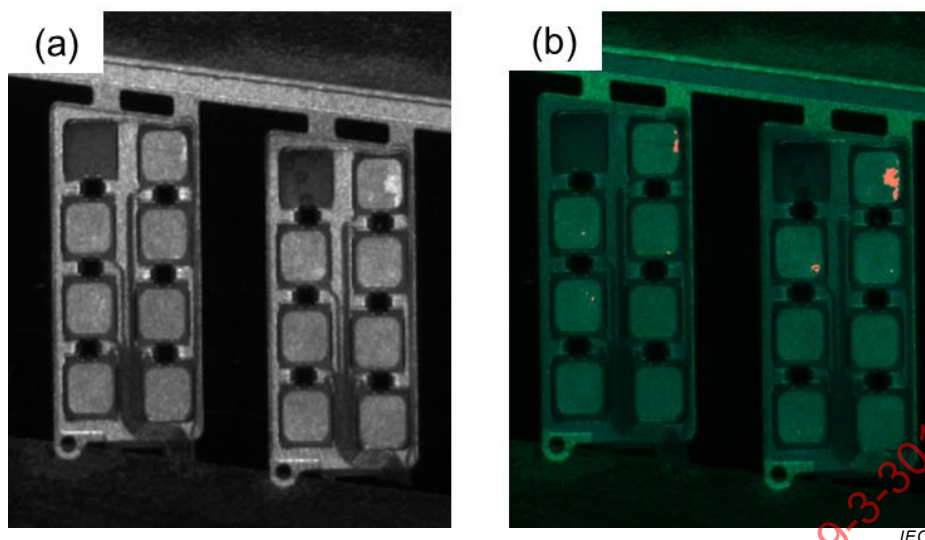


Figure B.2 a) – G/R colour distribution

Figure B.2 b) – Threshold images

Figure B.2 – Images of colour distribution

B.2 Feature extraction and discriminant analysis

Figure B.3 shows an example of frequency analysis result of the feature quantity extracted from gold-plating with colour non-uniformity as shown in Figure B.2. For the feature quantity, the number of times that the images were contracted is used to count the numbers of pixels remaining in the resulted images. This extracting method is found to be suitable comparing to the method using the length of diagonals in roughness mode irregularities shown in Figure A.4 b). The classification of the quality has been performed by visual inspection of skilled testers in advance.

Figure B.3 illustrates an example of a frequency analysis of the feature quantity of gold-plating in non-defective (No.1-84) and defective specimens (No.85-105) with colour non-uniformity. For the feature quantity, the number of times that the images were contracted is used to count the numbers of pixels remaining in the resulting images.

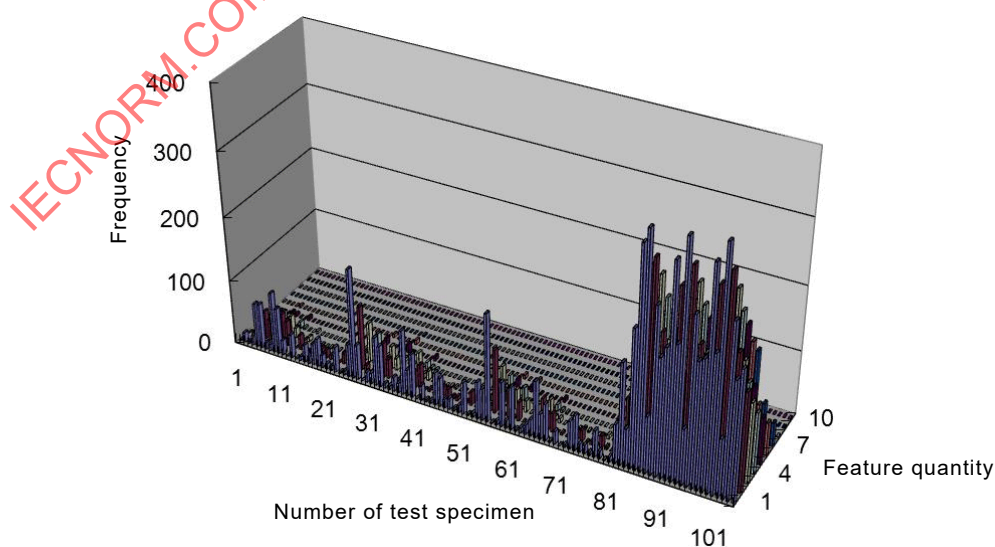


Figure B.3 – Frequency analysis example of a feature quantity