

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

AS22759/16

FEDERAL SUPPLY CLASS
6145


NOTICE

THIS DOCUMENT HAS BEEN TAKEN DIRECTLY FROM U.S. MILITARY SPECIFICATION MIL-W-22759/16A AND CONTAINS ONLY MINOR EDITORIAL AND FORMAT CHANGES REQUIRED TO BRING IT INTO CONFORMANCE WITH THE PUBLISHING REQUIREMENTS OF SAE TECHNICAL STANDARDS. THE INITIAL RELEASE OF THIS DOCUMENT IS INTENDED TO REPLACE MIL-W-22759/16A. ANY PART NUMBERS ESTABLISHED BY THE ORIGINAL SPECIFICATION REMAIN UNCHANGED.

THE ORIGINAL MILITARY SPECIFICATION WAS ADOPTED AS AN SAE STANDARD UNDER THE PROVISIONS OF THE SAE TECHNICAL STANDARDS BOARD (TSB) RULES AND REGULATIONS (TSB 001) PERTAINING TO ACCELERATED ADOPTION OF GOVERNMENT SPECIFICATIONS AND STANDARDS. TSB RULES PROVIDE FOR (A) THE PUBLICATION OF PORTIONS OF UNREVISED GOVERNMENT SPECIFICATIONS AND STANDARDS WITHOUT CONSENSUS VOTING AT THE SAE COMMITTEE LEVEL, AND (B) THE USE OF THE EXISTING GOVERNMENT SPECIFICATION OR STANDARD FORMAT.

UNDER DEPARTMENT OF DEFENSE POLICIES AND PROCEDURES, ANY QUALIFICATION REQUIREMENTS AND ASSOCIATED QUALIFIED PRODUCTS LISTS ARE MANDATORY FOR DOD CONTRACTS. ANY REQUIREMENT RELATING TO QUALIFIED PRODUCTS LISTS (QPL'S) HAS NOT BEEN ADOPTED BY SAE AND IS NOT PART OF THIS SAE TECHNICAL DOCUMENT.

THIRD ANGLE PROJECTION



PREPARED BY SAE SUBCOMMITTEE AE-8D

SAE Aerospace
An SAE International Group

AEROSPACE STANDARD

WIRE, ELECTRIC, FLUOROPOLYMER-INSULATED,
EXTRUDED ETFE, MEDIUM WEIGHT, TIN-COATED
COPPER CONDUCTOR, 600-VOLT, 150°C

AS22759/16
SHEET 1 OF 5

ISSUED 2001-07 REAFFIRMED 2008-03

Copyright 2008 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.


TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Fax: 724-776-0790

Tel: 724-776-4970 (outside USA)
Email: CustomerService@sae.org

SAE WEB ADDRESS: <http://www.sae.org>

The complete requirements for procuring the wire described herein shall consist of this document and the issue in effect of Specification MIL-W-22759.

AS22759/16

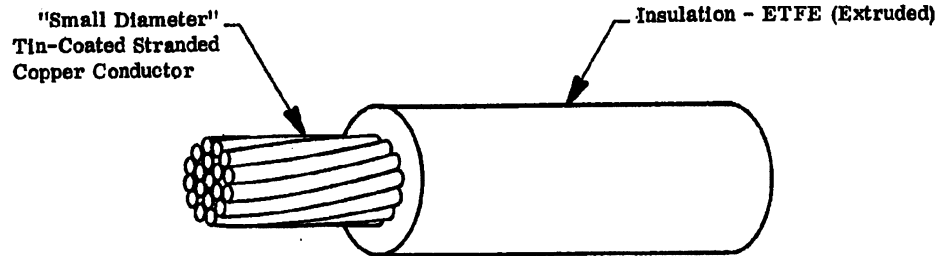

ETFE - Ethylene-Tetrafluoroethylene Copolymer

TABLE I. CONSTRUCTION DETAILS.

Part No. 1/	Wire size	Stranding (Number of strands X AWG gage of strands)	Diameter of stranded conductor (inches)		Finished wire		
			(min)	(max)	Resistance at 20°C (68°F) (ohms/1000 ft) (max)	Diameter (inches)	Weight (lbs/1000 ft) (max)
M22759/16-24-*	24	19 X 36	.023	.024	26.2	.045 ±.002	2.57
M22759/16-22-*	22	19 X 34	.029	.031	16.2	.052 ±.002	3.68
M22759/16-20-*	20	19 X 32	.037	.039	9.88	.060 ±.002	5.36
M22759/16-18-*	18	19 X 30	.046	.049	6.23	.071 ±.002	7.89
M22759/16-16-*	16	19 X 29	.052	.055	4.81	.079 ±.002	9.95
M22759/16-14-*	14	19 X 27	.065	.069	3.06	.093 ±.002	14.9
M22759/16-12-*	12	37 X 28	.084	.089	2.02	.114 ±.003	22.6
M22759/16-10-*	10	37 X 26	.106	.112	1.26	.139 ±.003	35.1
M22759/16-8-*	8	133 X 29	.158	.169	.701	.199 ±.003	63.5
M22759/16-6-*	6	133 X 27	.198	.212	.445	.250 ±.003	99.9
M22759/16-4-*	4	133 X 25	.250	.268	.280	.312 ±.004	157.
M22759/16-2-*	2	665 X 30	.320	.340	.183	.388 ±.004	245.
M22759/16-1-*	1	917 X 30	.360	.380	.149	.431 ±.005	314.
M22759/16-01-*	0	1045 X 30	.395	.425	.116	.479 ±.006	391.
M22759/16-02-*	00	1330 X 30	.440	.475	.091	.546 ±.007	504.

1/ PART NO.: The asterisks in the part number column, Tables I and II, shall be replaced by color code designators in accordance with MIL-STD-681. Examples: Size 20, white - M22759/16-20-9; white with orange stripe - M22759/16-20-93.

TABLE II. BEND TEST MANDRELS AND TEST LOADS.

Part No.	Mandrel diameter (inches) ($\pm 3\%$)			Test load (lbs) ($\pm 3\%$)	
	Life cycle test and short-term thermal stability test <u>1</u> /	Cold bend test	Wrap test <u>2</u> /	Life cycle test and short-term thermal stability test <u>1</u> /	Cold bend test
M22759/16-24-*	.50	1.00	-	0.5	3.0
M22759/16-22-*	.75	1.00	-	1.5	3.0
M22759/16-20-*	.75	1.00	-	2.0	4.0
M22759/16-18-*	1.00	1.25	-	2.0	4.0
M22759/16-16-*	1.00	1.25	-	2.0	5.0
M22759/16-14-*	1.25	2.00	-	2.0	5.0
M22759/16-12-*	2.00	2.00	-	2.0	5.0
M22759/16-10-*	3.00	3.00	-	2.0	5.0
M22759/16-8-*	3.00	4.00	-	3.0	6.0
M22759/16-6-*	4.00	5.00	-	3.0	10.0
M22759/16-4-*	5.00	6.00	-	3.0	10.0
M22759/16-2-*	6.00	8.00	1.25	4.0	15.0
M22759/16-1-*	8.00	10.0	1.25	4.0	15.0
M22759/16-01-*	8.00	10.0	1.75	4.0	15.0
M22759/16-02-*	10.0	14.0	1.75	6.0	20.0

1/ Also for bend tests after immersion.

2/ Use mandrel for wire sizes 2 and larger in "wrap back" test.

WIRE RATINGS AND ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 150°C (302°F) max conductor temperature

VOLTAGE RATING: 600 volts (rms) at sea level

SHORT-TERM THERMAL STABILITY: 7 hours at $230 \pm 2^\circ\text{C}$ ($446 \pm 3.6^\circ\text{F}$). Quality conformance test, Group II; test procedures and requirements as in life cycle test except for time and temperature of oven exposure

ACID RESISTANCE: No requirement

BLOCKING: $200 \pm 2^\circ\text{C}$ ($392 \pm 3.6^\circ\text{F}$)

COLOR: In accordance with MIL-STD-104, Class 1; white preferred

COLOR STRIPING OR BANDING DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight

DIELECTRIC TEST AFTER IMMERSION: 2200 volts (rms), 60Hz

FLAMMABILITY:

Vertical flame test (see page 4); 2 sec (max) after-flame, 5.50 in. (max) burn length

Post-flame dielectric test not required

HUMIDITY RESISTANCE: After humidity exposure, wire shall meet the requirements for initial insulation resistance.

IDENTIFICATION OF PRODUCT: Required

IDENTIFICATION DURABILITY: 125 cycles (250 strokes) (min), 500 grams weight

IMPULSE DIELECTRIC TEST: 8.0 kilovolts (peak), 100% test

INSULATION RESISTANCE, INITIAL:

Sizes 24 through 14: 5000 megohms for 1000 ft (min)

Sizes 12 through 6: 3000 megohms for 1000 ft (min)

Sizes 4 through 00: 2000 megohms for 1000 ft (min)

LIFE CYCLE:

Oven temperature, 200 \pm 2°C (392 \pm 3.6°F)

Dielectric test, 2200 volts (rms), 60Hz

LOW TEMPERATURE (COLD BEND):

Bend temperature: -65 \pm 2°C (-85 \pm 3.6°F)

Dielectric test, 2200 volts (rms), 60Hz

SHRINKAGE: 0.125 inch max at 200 \pm 2°C (392 \pm 3.6°F)

SMOKE: 200°C (392°F)

SPARK TEST OF PRIMARY INSULATION: Not required

SURFACE RESISTANCE:

Sizes 24 through 12: 500 megohm-inches (min), initial and final readings

Sizes 10 through 00: No requirement

THERMAL SHOCK:

Oven temperature, 150 \pm 2°C (302 \pm 3.6°F)

Max change in measurement:

Sizes 24 through 12: 0.060 inch

Sizes 10 through 8: 0.100 inch

Sizes 6 through 00: 0.125 inch

WICKING: No requirement

WIRE LENGTH REQUIREMENTS: Schedule A (See wire length schedules in MIL-W-22759)

WRAP TEST:

"Wrap back" test required; no cracking (See Table II, Note 2)

Oven temperature, 200 \pm 2°C (392 \pm 3.6°F)

INTENDED USE NOTE: The wire of this specification sheet is intended for interconnecting and hookup applications.

VERTICAL FLAME TEST

APPARATUS - The flammability test chamber shall be approximately one foot square by two feet in height and shall be open at the top and front to provide adequate ventilation for combustion but prevent drafts. Inside the chamber, near the open top, a clamp shall be provided from which the wire specimen may be suspended vertically about six inches in front of the rear wall of the chamber and equidistant from the two sides. The test burner shall be a Bunsen type gas burner having a 1/4 inch inlet, a bore of 3/8 inch nominal, and a length of approximately 4 inches above the primary air inlets. The burner shall be capable of providing the specified test flame, which shall be a 3-inch flame with an inner cone approximately one third of the total flame height and a temperature, at its hottest portion, of 1010 \pm 56°C (1850 \pm 100°F) as measured by a thermocouple pyrometer.

PROCEDURE - An 18 \pm 1/2 inch wire specimen marked 14 \pm 1/2 inches from its upper end to indicate where the test flame is to be applied, shall be suspended in the vertical position in the chamber and a weight equal to that specified for life cycle test of the same wire shall be attached to the lower end of the specimen to keep it taut during the flame exposure. With the test flame adjusted as specified in the preceding paragraph and with the burner held upright but inclined 20 degrees from vertical toward the specimen, the hottest portion of the flame shall be applied for 15 seconds to the approximate position of the test mark on the wire and shall then be withdrawn. The duration of flaming in the specimen after withdrawal of the gas test flame shall be timed and recorded in seconds. The burn length on the specimen as indicated by burned, charred, or melted insulation shall be measured and recorded to the nearest 1/8 inch. Areas of the specimen having the original insulation undamaged but covered with soot deposit removable by wiping or covered with material which has melted and flowed down the wire shall not be considered as part of the burn length. Breaking of the wire specimen in size 24 or smaller shall not be considered as failure. If breaking occurs in 3 or more specimens, a 22-gage specimen may be substituted for purposes of this test.